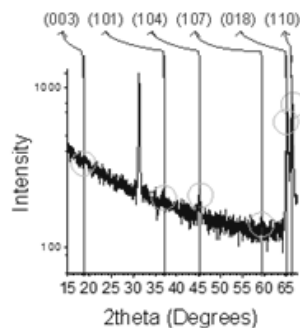


LAYERED MATERIALS FOR SOLID-STATE RECHARGEABLE LITHIUM BATTERIES

J.F. Ribeiro¹, M.F. Silva¹, L.M. Goncalves¹, M.M. Silva², J.P. Carmo¹ and J.H. Correia¹¹University of Minho, Algoritmi Centre, Campus Azurem, 4800-058 Guimaraes, Portugal²University of Minho, Chemistry Centre, Campus Gualtar, 4700-057 Braga, Portugal

Energy storage is mostly achieved with batteries and is a huge challenge of 21st century [1]. Despite the developments made by the microelectronic industry, the battery technology didn't follow these breakthroughs [2]. Batteries are ideal power source devices because they provide stable voltage and allow the leveling of energy consumption. This is of special concern when the target applications are in the biomedical field or for long cycle operations without requiring human activity [3, 4]. Solid-state film lithium batteries present the highest volumetric energy density (800 Whl⁻¹) and gravimetric energy density (350 Whg⁻¹), very high cycle life and charge-discharge rates up to 5C (only exceeded by super-capacitors) [4, 6]. The integration of batteries with solid-state circuits requires the use of solid-state anode, cathode and electrolyte. These batteries are intrinsically safe since all materials are solid and no leaking or explosion could occur. Film battery chemistry is being developed at ORNL (Oak Ridge National Laboratories) [3] with a solid electrolyte between the anode and cathode. These batteries have a potential of 4.5 V, typical capacities below 100 μAcm^{-2} and charge times of 2C to 5C. However, due to the process of thin-films deposition, the thickness is limited to few micrometers, resulting in a small capacity.

This work presents a cathode of lithium cobalt oxide (LiCoO₂), and electrolyte of lithium phosphate nitride (LIPON) and an anode of metallic lithium (Li). The LiCoO₂ is mostly used as cathode material in lithium batteries due to its excellent electrochemical stability, high capacity of lithium-ion diffusion and provide a high voltage to the battery. The fully crystalline structure facilitates the diffusivity of lithium ions and decreases the resistivity of the LiCoO₂. The LiCoO₂ film was deposited by RF sputtering and presented the best characteristics with a power source of 150 W, a pressure of 2×10^{-3} mbar, 40 sccm of argon and an annealing at 650 °C for two hours in vacuum. Electrical resistivity of 3.7 Ωmm was achieved and crystallization proven by XRD technique (Fig. 1).

Fig. 1: LiCoO₂ XRD.

LIPON is a glassy electrolyte and must have a high ionic conductivity and high electrical resistivity. It has an

electrical resistivity greater than $10^{14} \Omega$ and has an ionic conductivity of $6.3 \times 10^{-7} \text{ Scm}^{-1}$ for a temperature of 26 °C (Fig. 2). The LIPON was deposited by RF sputtering with a power source of 150 W, pressure of 3×10^{-4} mbar and 20 sccm of nitrogen.

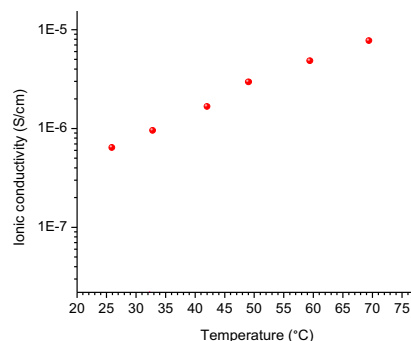


Fig. 2: LIPON ionic conductivity.

Although the oxidation in contact with air, the lithium metal is the most common material used as battery anode due to the high amount of lithium ions that can provide to battery discharge. This was deposited by thermal evaporation and its resistance measured during the deposition. A resistance of about 3.5 Ω was measured. The whole battery design, including the substrate (Si+Al₂O₃) and current collector's thin-films (Ti) is presented in Fig. 3.

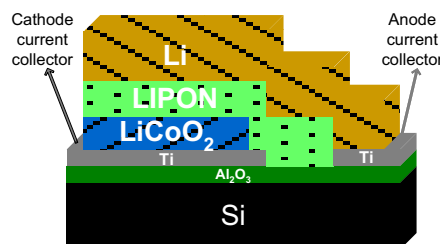


Fig. 3: Battery design (not on scale for better visualization).

Acknowledgements

This work was financially supported by FEDER/COMPETE and FCT funds with the project PTDC/EEA-ELC/114713/2009 and with first author scholarship SFRH/BD/78217/2011.

References

- [1] Shinya Suzuki, Naoko Sakai and Masaru Miyayama, Fabrication of titanate thin film by electrophoretic deposition of tetratanate nanosheets for electrodes of Li-ion battery, *Key Engineering Materials*, 388 (2009) 37-40.
- [2] M. Armand and J.M. Tarascon, Building better batteries, *Nature*, 451 (2008) 652 – 657.
- [3] N.J. Dudney and B.J. Neudecker, Solid state thin films lithium battery systems, *Solid State & Materials Science*, 4 (1999) 479-482.
- [4] B. Kang and G. Ceder, Battery materials for ultrafast charging and discharging, *Nature*, 458 (2009) 190.
- [5] N.J. Dudney, Solid-state thin-film rechargeable batteries, *Materials Science and Engineering - B*, 116 (2005) 245-249.
- [6] A. Patil, et al., Issue and challenges facing rechargeable thin film lithium batteries, *Materials Research Bulletin*, 43 (2008) 1913-1942.